

MICROCOPY RESOLUTION TEST CHART NATIONAL BUREAU OF STANDARDS-1963-A

Unclassified SECURITY CLASSIFICATION OF THIS PAGE (When Date	Entered)	(2) (2
REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
T. REPORT NUMBER $ au_{\mu}=16$	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Substite) EXAFS OF MONOLAYERS ON SILVER ELECTRODES 1984 Progress Report for SSRL Proposal No. 717M 7. AUTHOR(s) D. E. Reisner, O. R. Melroy, J. G. Gordon II, D. A. Buttry, G. L. Borges, L. Blum		5. Type of Report a Period Covered Technical Report 1-83 to 12-84 6. Performing org. Report Number
		S. CONTRACT OR GRANT NUMBER(#) NOO014-81-C-0776
PERFORMING ORGANIZATION NAME AND ADDRESS IBM Research Laboratory 5600 Cottle Road San Jose, CA 95193		10. PROGRAM ELEMENT PROJECT, TASK AREA & WORK UNIT NUMBERS
Office of Naval Research 800 N. Quincy Street Arlington, VA 22217 MONITORING AGENCY NAME & ADDRESS(if different from Controlling Office)		12. REPORT DATE January 8, 1985 13. NUMBER OF PAGES 3 15. SECURITY CLASS. (a) this report) Unclassified
		15a. DECLASSIFICATION DOWNGRADING SCHEDULE
This document has been approved to distribution is unlimited.		
TO THE PLEMENTARY NOTES		FEDE

To be published in the 1984 SSRL Activity Report

TV NORDS Continue on reverse side if necessary and identify by block numbers
Surface TMAFS, fluorescence detection, silver electrode, lead underpotential

During our latest run, November '83, at the Stanford Synchrotron Radiation Laboratory, we were able to detect x-ray fluorescence from a monolayer of Pb on single crystal silver film. The jump at the Pb edge represented increase in count rate of 150 eps on a 1500 cps background. This signal is too small for useful EXAFS to be extracted with a reasonable data collection time, but planned improvements in the electronic instrumentation and the experimental setup will achieve an edge jump greater than 1000 cps on a comparable background.

DD . TAN TE 1473 EDITION OF 1 NOV 65 15 OBSOLETE

deposition, synchrotron radiation

Unclassified

OFFICE OF NAVAL RESEARCH

Contract N00014-81-C-0776

TECHNICAL REPORT NO. 16

EXAFS OF MONOLAYERS ON SILVER ELECTRODES 1984 Progress Report for SSRL Proposal No. 717M

by

D. E. Reisner, O. R. Melroy, J. G. Gordon II, D. A. Buttry, G. L. Borges, L. Blum

Prepared for Publication

in

1984 SSRL Activity Report

IBM Research Laboratory San Jose, California 95193

and

University of Puarto Rico Rio Piedras, Puerto Rico 00931 Accession For

MTIS GRA&I
DTIC TAB
Unannounced
Justification

By____
Distribution/
Availability Codes

Avail and/or
Dist Special

January 8, 1984



Reproduction in whole or in part is permitted for any purpose of the United States Government

This document has been approved for public release and sale: its distribution is unlimited

RJ 4582 (49120) 1/28/85 Chemistry

EXAFS OF MONOLAYERS ON SILVER ELECTRODES 1984 Progress Report for SSRL proposal No 717M

D. E. Reisner, O. R. Melroy, J. G. Gordon, D. A. Buttry, G. L. Borges IBM San Jose Research Laboratory San Jose, California 95193

and

L. Blum University of Puerto Rico Rio Piedras, Puerto Rico 00931

Abstract:


During our latest run, November '83, at the Stanford Synchrotron Radiation Laboratory, we were able to detect x-ray fluorescence from a monolayer of Pb on single crystal silver film. The jump at the Pb edge represented increase in count rate of 150 cps on a 1500 cps background. This signal is too small for useful EXAFS to be extracted with a reasonable data collection time, but planned improvements in the electronic instrumentation and the experimental setup will achieve an edge jump greater than 1000 cps on a comparable background.

Our current knowledge of the electrochemical interface is derived primarily from thermodynamic and kinetic measurements coupled with theoretical treatments based on highly idealized models which describe only the diffuse double layer, or space charge region, within 20-100 Å of the electrode surface. These types of measurements do not yield unambiguous information about the structure of the interface at the atomic or molecular level. This situation is not attributable to lack of interest but rather to the lack of structure sensitive techniques which can be used in solution.

Surface EXAFS is potentially such a technique since X-rays are able to penetrate condensed matter. Utilizing the intense radiation available from a synchrotron and fluorescence detection, it should be possible to observe EXAFS of a monolayer of atoms at a metal:liquid interface, without having to remove the electrode from solution.

As a demonstration experiment, we have chosen to study a monatomic layer of lead, prepared by electrochemical underpotential deposition (UPD), on silver. Electrochemical deposition of lead on silver occurs in stages. The first monolayer is deposited at a potential which is less negative (by several hundred mV - the underpotential) than the expected thermodynamic deposition potential and the lead coverage remains constant at one monolayer over a relatively wide potential range.

During our last run, November '83, we were able to detect fluorescence from a monolayer of Pb on single crystal silver film, but at a signal level too weak to permit meaningful analysis. The observed spectrum, normalized to incident x-ray flux is displayed in the Figure. This spectrum is a composite of 15 scans of 30 min duration each (45 sec/point). The edge jump corresponds to an increase in count rate of 150 cps on a 1500 cps background.

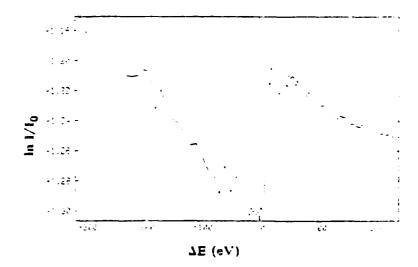

The substrate was a free standing 2 µm Ag(111) film prepared by epitaxial deposition on mica. The fluorescence data was collected using a 2" diameter NaI(Tl) scintillator preceded by an Se filter and Soller slits, and operated with a very narrow discriminator window. Despite its poor energy resolution, its large active area and high count rate

capability provided a better S/N than a smaller HPGe detector whose throughput was limited by the detection electronics (the total count rate, pre-discriminator, was > 100 Kcps).

Measurements made with the energy dispersive HPGe detector verified that the major contributions to background were elastic and Compton scatter from the substrate followed by impurity fluorescence and Se fluorescence from the filter. Planned improvements in the electronic instrumentation and the experimental setup, we believe, will achieve an edge jump of > 1000 cps on a comparable background.

This work was supported in part by the Office of Naval Research.

END

FILMED

3-85

DTIC